


	FORMAPPROVED
OCD _{ICD} .	HOBBSOM B No 1004-0137 Expires: March 31, 200

	BUREAU OF LAND MANAGEMEN'	Γ	5. Lease Serial No.
SUNDRY	NOTICES AND REPORTS	ON WELLS	LC-057210
SEP To an active the	nis form for proposals to drill or ell. Use Form 3160-3 (APD) for	to re-enter an	6. If Indian, Allottee or Tribe Name
SUBMIT IN TRI	PLICATE - Other instructions of	on reverse side.	7. If Unit or CA/Agreement, Name and/or No
1. Type of Well X Oil Well	Gas Well X Other		8. Well Name and No.
2 Name of Operator	. (#017017)		MCA 9. API Well No.
ConocoPhillips Company 3a. Address		No.(include area code)	.0.11
3300 N. "A" Street, Bldg.	6, Midland TX 79705 (432)688-6884	10. Field and Pool, or Exploratory Area
	c., T., R., M., or Survey Description)	,	Maljamar; Grayburg-San Andres
T-17-S, R-32-E & R-33-E			11. County or Parish, State Lea New Mexico
12. CHECK AF	PPROPRIATE BOX(ES)TO INDICATE	E NATURE OF NOTICE, RI	EPORT, OR OTHER DATA
TYPE OF SUBMISSION		TYPEOF ACTION	í
Notice of Intent	Acidize Deepen AlterCasing Fracture Casing Repair New Con		Well Integrity
Subsequent Report	[TY 7]	struction Recomplete Abandon Temporarily Aba	Other
Final Abandonment Notice	Convert to Injection PlugBack		HIGON
testing has been completed. Fin determined that the site is ready Ref. Bond #ES0085 Referencing Master Drilli	al Abandonment Notices shall be filed only afte	r all requirements, including reclam	n a new interval, a Form 3160-4 shall be filed once nation, have been completed, and the operator has //2008. ConocoPhillips wishes to Orilling Plant
Pg. 7 8-5/8" Surf. Csg. Pg. 7 WOC time chan Pg. 8 5-1/2" Prod. Csg	. Lead Slurry Density Change fro ge from 24 to 18 hrs. J. Tail Slurry Density Change fron	m 13.1 to 13.5 ppg	APPROVED
Pg. 11 5-1/2" Prod. Csg	 Tail Slurry Density Change fron Tail Slurry Density Change fron hed for your convience to insert in 	n 16.4 to 14.8 ppg	SEP 2 2008
	•		LES BABYAK
14. I hereby certify that the forego	this request is greatly appreciate	<u> </u>	PETROLEUM ENGINEER
Name (Printed/Typed)			Committee of the second state of the second
Celeste G. Dale		Title Regulatory Spec	ialist
Signature (select	Aulali	Date 06/16/2008	<u> </u>
	THIS SPACE FOR FEDERAL	OR STATE OFFICE L	JSE
Approved by		Title	Date
Conditions of approval, if any, are a	ttached. Approval of this notice does not warra or equitable title to those rights in the subject o conduct operations thereon.	ant or /	Z
itle 18 U.S.C. Section 1001 and Title tates any false, fictitious or fraudu	e 43 U.S.C. Section 1212, make it a crime for an ilent statements or representations as tolany i	y person knowingly and willfully to matter within its jurisdiction.	o make to any department or agency of the United

(Instructions on page 2)

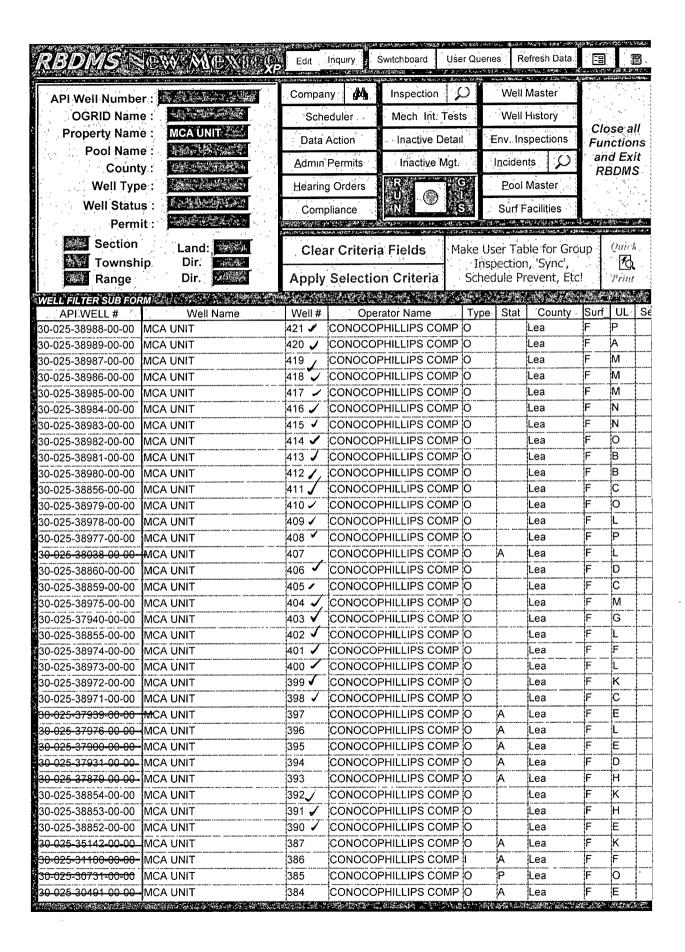

4. Proposed cementing program:

For the cementing program a range is presented for the number of sacks of cement and for the bottom, top, and length of the lead slurries and tail slurries due to the variation in formation tops and planned TD for the planned / contemplated wells for which this Master Drilling Plan is intended.

13-3/8" Conductor:

Cement to surface with ready mix or Class C Neat cement. TOC at surface.

8-5/8" Surface Casing:

The intention for the cementing program for the Surface Casing is to:

- Place the Tail Slurry from the casing shoe to 300' above the casing shoe,
- Bring the Lead Slurry to surface.

Spacer: 20 bbls Fresh Water

Volume (sx)	Bottom	Top	Length	Density	Yield	Mix Wtr	Compressive Strengths	
& Recipe & Excess %	(ft MD)	(ft MD)	(ft)	(ppg)	(cuft/sx)	gal/sx	@ 85 deg F by UCA Meth	
185 – 535 sx Class C + 6% bentonite + 2% CaCl2 + 0.125% Polyflake	325 to 940	Surface	325 to 940	13.5	1.96	10.69	Time 12 hrs 18 hrs 24 hrs	Strength 316 psi 417 psi 506 psi

Tail Slurry								
Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strengths @ 91 deg F by UCA Meth	
220 sx Class C + 2% CaCl2 + 0.125% Polyflake Excess = 100%	625' to 1240'	325' to 940'	300'	14.8	1.35	6.36	Time 3 hrs 9 hrs 12 hrs 24 hrs 48 hrs	Strength 50 psi 500 psi 793 psi 1266 psi 2183 psi

Displacement: Fresh Water

Note: In accordance with the Pecos District Conditions of Approval, we will Wait on Cement (WOC) for a period of not less than 18 hrs after placement of the cement on the Surface Casing in order to achieve at least 500 psi compressive strength in both the Lead Slurry and Tail Slurry cements prior to drilling out of the Surface Casing.

5-1/2" Production Casing Cementing Program - Single Stage Cementing Option:

The intention for the cementing program for the Production Casing – Single Stage Cementing Option is to:

- Place the Tail Slurry from the casing shoe to the top of the Grayburg formation,
- Bring the Lead Slurry to surface.

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water.

Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Stre @ 113	oressive engths deg F by Method
433 – 644 sx 50% Class C 50% POZ + 10% bentonite + 8 lb/sx Salt + 0.2% Fluid Loss Additive + 0.125% Polyflake	3270' to 3940'	Surface	3270' to 3940'	11.8	2.55	14.88	Time 12 hrs 24 hrs 48 hrs 72 hrs	Strength 100 psi 200 psi 245 psi 310 psi

Volume (sx)	Bottom	Top	Length	Density	Yield	Mix Wtr	Compressive Strengths @ 115 deg F by UCA Metho	
& Recipe & Excess %	(ft MD)	(ft MD)	(ft)	(ppg)	(cuft/sx)	gal/sx		
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: 2% KCL water with approximately 250 ppm gluteraldehyde biocide.

5-1/2" Production Casing Cementing Program - Two-Stage Cementing Option (for Loss of Circulation Events):

We propose an option to use the two-stage cementing method for cementing the production casing if any loss of circulation events or heavy seepage is experienced while drilling the 7-7/8" hole. (see discussion in Item 3 above). The proposed two-stage cementing program would be as follows:

- Stage 1: Would place cement from the casing shoe to the stage tool.
- Stage 2: Would place cement from the stage tool to Surface.

Stage 1:

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water

Stage	1 - L	ead Surry	: None

Volume (sx)	Bottom	Top	Length	Density	Yield	Mix Wtr	Compressive Strengths @ 113 deg F by Crush Metl	
& Recipe & Excess %	(ft MD)	(ft MD)	(ft)	(ppg)	(cuft/sx)	gal/sx		
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: A volume of Fresh Water equal to the capacity volume from the stage tool to the float collar, followed by brine based mud.

5-1/2" Production Casing Cementing Program – Two-Stage Cementing Option with Stage Tool and External Casing Packers (for Water Flow Events):

We propose an option to use the two-stage cementing method with a Stage Tool and two each External Casing Packers if any waterflow event is experienced while drilling the 7-7/8" hole as discussed above in Item 3. The proposed two-stage cementing program would be as follows:

- Stage 1: Would place cement from the casing shoe to the stage tool
- Stage 2: Would place cement from the stage tool to Surface.

Stage 1:

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water

Stage 1 – Lead Slurry	,				T		T	
Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive @ 113 deg F by (
77 – 363 sx 50% Class C 50% POZ + 10% bentonite + 8 lb/sx Salt + 0.2% Fluid Loss Additive + 0.125% Polyflake	3270' to 3940'	1670' to 3440'	500' to 1600'	11.8	2.55	14.88	Time 12 hrs 24 hrs 48 hrs 72 hrs	Strength 100 psi 200 psi 245 psi 310 psi

Stage 1 – Tail Slurry Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strengths @ 113 deg F by Crush Met	
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: A volume of Fresh Water equal to the capacity volume from the stage tool to the float collar, followed by brine based mud.