
The Leve	UNITEDSTATES SEPARTMENT OF THE INTERIO BUREAU OF LAND MANAGEMENT	~~~ n 1).	HOBBS xpires: March 31, 2007
			5. Lease Serial No.
	NOTICES AND REPORTS		LC-057210
Debandoned w	is form for proposals to drill or gll. Use Form 3160-3 (APD) for s	to re-enter an such proposals.	6. If Indian, Allottee or Tribe Name
	PLICATE - Other instructions of	on reverse side.	7. If Unit or CA/Agreement, Name and/or No.
1. Type of Well X Oil Well	Gas Well X Other		8. Well Name and No.
2. Name of Operator Conoco Phillips Company	v (#217817)		9. API Well No.
3a. Address 3300 N. "A" Street, Bldg.	3b. Phone!	No.(include area code))688-6884	30-025- See AHack 10. Field and Pool, or Exploratory Area
	c., T., R., M., or Survey Description)	7000 000+	Maljamar; Grayburg-San Andres
	·		11. County or Parish, State
T-17-S, R-32-E & R-33-E	•		Lea New Mexico
12. CHECK AI	PPROPRIATE BOX(ES)TO INDICATE	E NATURE OF NOTICE, RI	EPORT, OR OTHER DATA
TYPE OF SUBMISSION		TYPEOF ACTION	1
X Notice of Intent	Acidize Deepen AlterCasing Fracture	Production (Sta	rt/Resume) Water Shut-Off Well Integrity
Subsequent Report	Casing Repair New Con		Other
Final Abandonment Notice	X Change Plans □ Plugand. □ Convert to Injection □ PlugBacl	-	andon
following completion of the inv	volved operations. If the operation results in a mutal Abandonment Notices shall be filed only after	ltiple completion or recompletion i	red subsequent reports shall be filed within 30 days in a new interval, a Form 3160-4 shall be filed once nation, have been completed, and the operator has
Ref. Bond #ES0085			•
	ing Plan on file with the BLM Car lifications to the cement program		
	. Lead Slurry Density Change fro ge from 24 to 18 hrs.	m 13.1 to 13.5 ppg	APPROVED
	g. Tail Slurry Density Change fron	n 16.4 to 14.8 ppg	1 / THOUSE
Pg. 9 5-1/2" Prod. Csc	 Tail Slurry Density Change from 	n 16.4 to 14.8 ppg	
•	g. Tail Slurry Density Change from	: 5	SEP 2 2008
Updated pages are attac	hed for your convience to insert i	nto the master docume	LES BABYAK
	this request is greatly appreciate	ed. <u> </u>	PETROLEUM ENGINEER
14. I hereby certify that the foreg Name (Printed/Typed)	oing is true and correct		The state of the s
Celeste G. Dale		Title Regulatory Spec	cialist
Signature (allet	e dulale	Date 06/16/2008	
•	THIS SPACE FOR FEDERAL	OR STATE OFFICE	JSE
Approved by		Title	Date
	attached. Approval of this notice does not warra	. 1 · /	
which would entitle the applicant	or equitable title to those rights in the subject to conduct operations thereon.	lease Office	7

Title 18 U.S.C. Section 1001 and Title 43 U.S.C. Section 1212, make it a crime for any person knowingly and willfully to make to any department or agency of the United States any false, fictitious or fraudulent statements or representations as to any matter within its jurisdiction.

(Instructions on page 2)

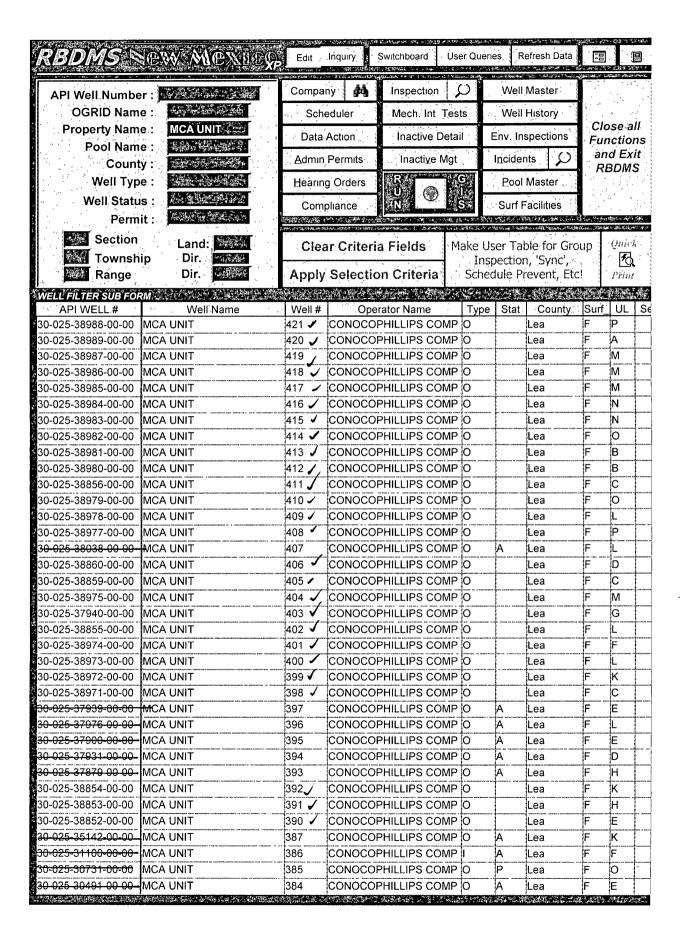

4. Proposed cementing program:

For the cementing program a range is presented for the number of sacks of cement and for the bottom, top, and length of the lead slurries and tail slurries due to the variation in formation tops and planned TD for the planned / contemplated wells for which this Master Drilling Plan is intended.

13-3/8" Conductor:

Cement to surface with ready mix or Class C Neat cement. TOC at surface.

8-5/8" Surface Casing:

The intention for the cementing program for the Surface Casing is to:

- Place the Tail Slurry from the casing shoe to 300' above the casing shoe,
- Bring the Lead Slurry to surface.

Spacer: 20 bbls Fresh Water

Lead Slurry								
Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strength @ 85 deg F by UCA Metl	
185 – 535 sx Class C + 6% bentonite + 2% CaCl2 + 0.125% Polyflake	325 to 940	Surface	325 to 940	13.5	1.96	10.69	Time 12 hrs 18 hrs 24 hrs	Strength 316 psi 417 psi 506 psi
Excess = 170%							,	

Tail Slurry								
Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx		ve Strengths by UCA Method
220 sx Class C + 2% CaCl2 + 0.125% Polyflake Excess = 100%	625' to 1240'	325' to 940'	300'	14.8	1.35	6.36	Time 3 hrs 9 hrs 12 hrs 24 hrs 48 hrs	Strength 50 psi 500 psi 793 psi 1266 psi 2183 psi

Displacement: Fresh Water

Note: In accordance with the Pecos District Conditions of Approval, we will Wait on Cement (WOC) for a period of not less than 18 hrs after placement of the cement on the Surface Casing in order to achieve at least 500 psi compressive strength in both the Lead Slurry and Tail Slurry cements prior to drilling out of the Surface Casing.

5-1/2" Production Casing Cementing Program - Single Stage Cementing Option:

The intention for the cementing program for the Production Casing – Single Stage Cementing Option is to:

- Place the Tail Slurry from the casing shoe to the top of the Grayburg formation,
- Bring the Lead Slurry to surface.

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water.

Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Stre @ 113	pressive engths deg F by Method
433 – 644 sx 50% Class C 50% POZ + 10% bentonite + 8 lb/sx Salt + 0.2% Fluid Loss Additive + 0.125% Polyflake	3270' to 3940'	Surface	3270' to 3940'	11.8	2.55	14.88	Time 12 hrs 24 hrs 48 hrs 72 hrs	Strength 100 psi 200 psi 245 psi 310 psi

Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strength @ 115 deg F by UCA Me	
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: 2% KCL water with approximately 250 ppm gluteraldehyde biocide.

5-1/2" Production Casing Cementing Program - Two-Stage Cementing Option (for Loss of Circulation Events):

We propose an option to use the two-stage cementing method for cementing the production casing if any loss of circulation events or heavy seepage is experienced while drilling the 7-7/8" hole. (see discussion in Item 3 above). The proposed two-stage cementing program would be as follows:

- Stage 1: Would place cement from the casing shoe to the stage tool.
- Stage 2: Would place cement from the stage tool to Surface.

Stage 1:

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water

Stage 1 - Lead Surry: None

Volume (sx)	Bottom	Top	Length	Density	Yield	Mix Wtr	Compressive	
& Recipe & Excess %	(ft MD)	(ft MD)	(ft)	(ppg)	(cuft/sx)	gal/sx	@ 113 deg F by	
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: A volume of Fresh Water equal to the capacity volume from the stage tool to the float collar, followed by brine based mud.

5-1/2" Production Casing Cementing Program – Two-Stage Cementing Option with Stage Tool and External Casing Packers (for Water Flow Events):

We propose an option to use the two-stage cementing method with a Stage Tool and two each External Casing Packers if any waterflow event is experienced while drilling the 7-7/8" hole as discussed above in Item 3. The proposed two-stage cementing program would be as follows:

- Stage 1: Would place cement from the casing shoe to the stage tool
- Stage 2: Would place cement from the stage tool to Surface.

Stage 1:

Spacer: 20 bbls Fresh Water with an option to follow this with 1000 gallons SuperFlush 102 and 20 additional bbls Fresh Water

Stage 1 - Lead Slurry					· · · · · ·		1	
Volume (sx) & Recipe & Excess %	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strengths @ 113 deg F by Crush Metho	
77 – 363 sx 50% Class C 50% POZ + 10% bentonite + 8 lb/sx Salt + 0.2% Fluid Loss Additive + 0.125% Polyflake	3270' to 3940'	1670' to 3440'	500' to 1600'	11.8	2.55	14.88	Time 12 hrs 24 hrs 48 hrs 72 hrs	Strength 100 psi 200 psi 245 psi 310 psi

Stage 1 – Tail Slurry Volume (sx) & Recipe & Excess %_	Bottom (ft MD)	Top (ft MD)	Length (ft)	Density (ppg)	Yield (cuft/sx)	Mix Wtr gal/sx	Compressive Strengths @ 113 deg F by Crush Me	
150 – 285 sx 65% Class C 35% POZ + 0.4% Dispersant	4155' to 4705'	3270' to 3940'	636' to 885'	14.8	0.98	3.76	Time 5 hrs 56 min 8 hrs 12 min 24 hrs 48 hrs 72 hrs	Strength 50 psi 500 psi 2806 psi 4690 psi 5661 psi

Displacement: A volume of Fresh Water equal to the capacity volume from the stage tool to the float collar, followed by brine based mud.