

(November 1994)

UNITED STATES
DEPARTMENT OF THE INTERIOR
BUREAU OF LAND MANAGEMENT

FORM APPROVED
OMB No. 1004-0135
Expires July 31, 1996

1625 N. French Dr.
Hobbs, NM 88240

SUNDRY NOTICES AND REPORTS ON WELLS

Do not use this form for proposals to drill or to re-enter an abandoned well. Use Form 3160-3 (APD) for such proposals.

SUBMIT IN TRIPLICATE - Other Instructions on reverse side

1. Type of Well

☐ Oil Well ☒ Gas Well ☐ Other

2. Name of Operator

Lynx Petroleum Consultants, Inc.

3a. Address

P.O. Box 1708, Hobbs, NM 88241

3b. Phone No. (include area code)

505-392-6950

4. Location of Well (Footage, Sec., T., R., M., or Survey Description)

U.L. "O", 990' FSL & 1650' FEL
Section 31, T-18S, R-32E

Lease Serial No.

NM 23006

6. If Indian, Allottee or Tribe Name

7. If Unit or CA/Agreement, Name and/or No.

8. Well Name and No.

Lusk 31 Federal #1

9. API Well No.

30-025-35073

10. Field and Pool, or Exploratory Area

Lusk Morrow, N.

11. County or Parish, State

Lea County, NM

12. CHECK APPROPRIATE BOX(ES) TO INDICATE NATURE OF NOTICE, REPORT, OR OTHER DATA

TYPE OF SUBMISSION

TYPE OF ACTION

☐ Notice of Intent

☒ Subsequent Report

☐ Final Abandonment Notice

☐ Acidize

☐ Alter Casing

☐ Casing Repair

☐ Change Plans

☐ Convert to Injection

☐ Deepen

☐ Fracture Treat

☐ New Construction

☐ Plug and Abandon

☐ Plug Back

☐ Production (Start/Resume)

☐ Reclamation

☐ Recomplete

☐ Temporarily Abandon

☐ Water Disposal

☐ Water Shut-Off

☐ Well Integrity

☒ Other Set 5 1/2" Casing

13. Describe Proposed or Completed Operation (clearly state all pertinent details, including estimated starting date of any proposed work and approximate duration thereof. If the proposal is to deepen directionally or recompleat horizontally, give subsurface locations and measured and true vertical depths of all pertinent markers and zones. Attach the Bond under which the work will be performed or provide the Bond No. on file with BLM/BIA. Required subsequent reports shall be filed within 30 day following completion of the involved operations. If the operation results in a multiple completion or recompleat in a new interval, a Form 3160-4 shall be filed once testing has been completed. Final Abandonment Notices shall be filed only after all requirements, including reclamation, have been completed, and the operator has determined that the site is ready for final inspection.)

10/2/00

T.D. 12620' 7 7/8" Hole.

Ran 5 1/2" casing as follows:

5 1/2", 17#, P-110, LT&C 0' - 1326'
5 1/2", 17#, L-80, LT&C 1326' - 10644'
5 1/2", 17#, P-110, LT&C 10644' - 12612'

Stage Collar @ 9505'

(See Attached for Cementing Details)

14. I hereby certify that the foregoing is true and correct
Name (Printed/Typed)

Marc Wise

Signature

Marc Wise

Title

President

Date

10/3/00

THIS SPACE FOR FEDERAL OR STATE OFFICE USE

ORIGINAL SIGNED BY CHRIS WILSON
DISTRICT SUPERVISOR

Title

Date OCT 19 2000

Conditions of approval, if any, are attached. Approval of this notice does not warrant or certify that the applicant holds legal or equitable title to those rights in the subject lease which would entitle the applicant to conduct operations thereon.

Office


Title 18 U.S.C. Section 1001, makes it a crime for any person knowingly and willfully to make to any department or agency of the United States any false, fictitious or fraudulent statements or representations as to any matter within its jurisdiction.

(Instructions on reverse)

ACCEPTED FOR RECORD
PETER W. CHESTER

OCT 11 2000

BUREAU OF LAND MANAGEMENT
ROSWELL RESOURCE AREA

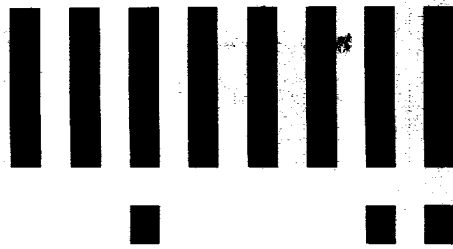

LTR



Job separation sheet

Lusk 31 Federal #1
Lynx Petroleum Consultants, Inc.
5 1/2" Casing Cementing Report

First Stage:

Pumped 675 sacks Super "H" Modified (61:15:11) Poz w/11# CSE
+ .8% FL-25 + 1% FL-62 mixed at 13.8 ppg (1.39 ft³/sx).
Opened Stage Collar and circulated out 113 sxs cement.

Second Stage:

Pumped 775 sxs lead slurry Class "C" (35:65) Poz + .25% Cello
Flak + .4% FL-25 + 6% Bentonite mixed at 12.7 ppg (1.85 ft³/sx).
Followed by 225 sxs tail slurry Class "H" mixed at 16.5 ppg
(1.05 ft³/sx).

Top of Cement at 3750' Temperature Survey.